



Hytrel® 5556

THERMOPLASTIC POLYESTER ELASTOMER

Common features of Hytrel® thermoplastic polyester elastomer include mechanical and physical properties such as exceptional toughness and resilience, high resistance to creep, impact and flex fatigue, flexibility at low temperatures and good retention of properties at elevated temperatures. In addition, it resists many industrial chemicals, oils and solvents. Special grades include heat stabilised, flame retardant, food contact compliant, blow molding and extrusion grades. Concentrates offered include black pigments, UV protection additives, heat stabilisers, and flame retardants. Hytrel® thermoplastic polyester elastomer is plasticiser free.

The good melt stability of Hytrel® thermoplastic polyester elastomer normally enables the recycling of properly handled production waste. If recycling is not possible, DuPont recommends, as the preferred option, incineration with energy recovery (-24 kJ/g of base polymer) in appropriately equipped installations. For disposal, local regulations have to be observed.

Hytrel® thermoplastic polyester elastomer typically is used in demanding applications in the automotive, fluid power, electrical/electronic, consumer goods, appliance and power tool, sporting goods, furniture, industrial and off-road transportation/equipment industry.

Hytrel® 5556 is a medium modulus Hytrel® grade with nominal durometer hardness of 55D. It contains non-discoloring stabilizer. It can be processed by many conventional thermoplastic processing techniques like injection moulding and extrusion. Typical applications: Hose and tubing, wire and cable, film and sheeting, belting.

Product information

Resin Identification	TPC-ET	ISO 1043
Part Marking Code	>TPC-ET<	ISO 11469

Rheological properties

Melt volume-flow rate	7 cm ³ /10min	ISO 1133
Melt mass-flow rate	7.8 g/10min	ISO 1133
Temperature	220 °C	ISO 1133
Load	2.16 kg	ISO 1133
Melt mass-flow rate, Temperature	220 °C	ISO 1133
Melt mass-flow rate, Load	2.16 kg	ISO 1133
Moulding shrinkage, parallel	1.4 %	ISO 294-4, 2577
Moulding shrinkage, normal	1.4 %	ISO 294-4, 2577

Typical mechanical properties

Tensile Modulus	180 MPa	ISO 527-1/-2
Yield stress	15 MPa	ISO 527-1/-2
Yield strain	40 %	ISO 527-1/-2
Stress at 5% strain	6.9 MPa	ISO 527-1/-2
Stress at 10% strain	11 MPa	ISO 527-1/-2



Hytrel® 5556

THERMOPLASTIC POLYESTER ELASTOMER

Stress at 50% strain	14.5 MPa	ISO 527-1/-2
Stress at 100% strain	16 MPa	ISO 527-1/-2
Stress at break	40 MPa	ISO 527-1/-2
Nominal strain at break	600 %	ISO 527-1/-2
Strain at break	>300 %	ISO 527-1/-2
Flexural Modulus	190 MPa	ISO 178
Tensile creep modulus, 1h	170 MPa	ISO 899-1
Tensile creep modulus, 1000h	133 MPa	ISO 899-1
Charpy impact strength, 23°C	N kJ/m ²	ISO 179/1eU
Charpy impact strength, -30°C	N kJ/m ²	ISO 179/1eU
Charpy notched impact strength, 23°C	N kJ/m ²	ISO 179/1eA
Charpy notched impact strength, -30°C	145 ^[P] kJ/m ²	ISO 179/1eA
Charpy notched impact strength, -40°C	145 kJ/m ²	ISO 179/1eA
Tensile notched impact strength, 23°C	320 kJ/m ²	ISO 8256/1
Puncture - maximum force, 23°C	2400 N	ISO 6603-2
Puncture - maximum force, -30°C	3700 N	ISO 6603-2
Puncture energy, 23°C	27 J	ISO 6603-2
Puncture energy, -30°C	43 J	ISO 6603-2
Izod notched impact strength, 23°C	N kJ/m ²	ISO 180/1A
Izod notched impact strength, -40°C	N kJ/m ²	ISO 180/1A
Poisson's ratio	0.48 -	
Brittleness temperature	-98 °C	ISO 974
Shore D hardness, 15s	51 -	ISO 48-4
Shore D hardness, max	55 -	ISO 48-4
Tear strength, parallel	137 kN/m	ISO 34-1
Tear strength, normal	134 kN/m	ISO 34-1
Abrasion resistance	120 mm ³	ISO 4649

[P]: Partial Break

Thermal properties

Melting temperature, 10°C/min	201 °C	ISO 11357-1/-3
Glass transition temperature, 10°C/min	-20 °C	ISO 11357-1/-2
Temp. of deflection under load, 1.8 MPa	45 °C	ISO 75-1/-2
Temp. of deflection under load, 0.45 MPa	70 °C	ISO 75-1/-2
Vicat softening temperature, 50°C/h, 50N	75 °C	ISO 306
Vicat softening temperature, 50°C/h 10N	180 °C	ISO 306
CLTE, Parallel, -40-23°C	160 E-6/K	ISO 11359-1/-2
Coeff. of linear therm. expansion, parallel	180 E-6/K	ISO 11359-1/-2
CLTE, Normal, -40-23°C	174 E-6/K	ISO 11359-1/-2
Coeff. of linear therm. expansion, normal	180 E-6/K	ISO 11359-1/-2
Thermal conductivity of melt	0.16 W/(m K)	
Eff. thermal diffusivity	7.0E-8 m ² /s	
Spec. heat capacity of melt	2110 J/(kg K)	
RTI, electrical, 0.75mm	85 °C	UL 746B
RTI, electrical, 1.5mm	85 °C	UL 746B



Hytrel® 5556

THERMOPLASTIC POLYESTER ELASTOMER

RTI, electrical, 3mm	85 °C	UL 746B
RTI, impact, 0.75mm	50 °C	UL 746B
RTI, impact, 1.5mm	85 °C	UL 746B
RTI, impact, 3mm	85 °C	UL 746B
RTI, strength, 0.75mm	50 °C	UL 746B
RTI, strength, 1.5mm	75 °C	UL 746B
RTI, strength, 3mm	80 °C	UL 746B

Flammability

Burning Behav. at 1.5mm nom. thickn.	HB class	IEC 60695-11-10
Thickness tested	1.5 mm	IEC 60695-11-10
UL recognition	yes -	UL 94
Burning Behav. at thickness h	HB class	IEC 60695-11-10
Thickness tested	3 mm	IEC 60695-11-10
UL recognition	yes -	UL 94
Oxygen index	20 %	ISO 4589-1/-2
Glow Wire Flammability Index, 2mm	700 ^[DS] °C	IEC 60695-2-12
Glow Wire Ignition Temperature, 2mm	675 ^[DS] °C	IEC 60695-2-13
Glow Wire Temperature, No Flame, 2mm	650 ^[DS] °C	IEC 60335-1
FMVSS Class	SE -	ISO 3795 (FMVSS 302)

[DS]: Derived from similar grade

Electrical properties

Relative permittivity, 100Hz	4.8 -	IEC 62631-2-1
Relative permittivity, 1MHz	4.4 -	IEC 62631-2-1
Dissipation factor, 100Hz	90 E-4	IEC 62631-2-1
Dissipation factor, 1MHz	375 E-4	IEC 62631-2-1
Volume resistivity	4E11 Ohm.m	IEC 62631-3-1
Surface resistivity	>1E15 Ohm	IEC 62631-3-2
Electric strength	19 kV/mm	IEC 60243-1
Comparative tracking index	600 -	IEC 60112

Other properties

Humidity absorption, 2mm	0.2 %	Sim. to ISO 62
Water absorption, 2mm	0.6 %	Sim. to ISO 62
Density	1190 kg/m ³	ISO 1183
Density of melt	1030 kg/m ³	
Water Absorption, Immersion 24h	0.6 %	Sim. to ISO 62



Hytrel® 5556

THERMOPLASTIC POLYESTER ELASTOMER

Film Properties

WVTR, 23°C/85%r.h.	300 g/(m ² *d)	DIS 15106-1/-2
Oxygen transmission rate, 23°C/85%r.h.	6000 cm ³ /(m ² *d*bar)	DIS 15105-1/-2
Thickness of specimen	0.025 mm	

VDA Properties

Emission of organic compounds	8.5 µgC/g	VDA 277
Odour	5 class	VDA 270
Fogging, G-value (condensate)	0.1 mg	ISO 6452

Injection

Drying Recommended	yes
Drying Temperature	100 °C
Drying Time, Dehumidified Dryer	2 - 3 h
Processing Moisture Content	≤0.08 %
Melt Temperature Optimum	230 °C
Min. melt temperature	220 °C
Max. melt temperature	250 °C
Mold Temperature Optimum	45 °C
Min. mould temperature	45 °C
Max. mould temperature	55 °C

Extrusion


Drying Temperature	90 - 110 °C
Drying Time, Dehumidified Dryer	2 - 3 h
Processing Moisture Content	≤0.06 %
Melt Temperature Optimum	225 °C
Melt Temperature Range	220 - 235 °C



Hytrel[®] 5556

THERMOPLASTIC POLYESTER ELASTOMER


Viscosity-shear rate

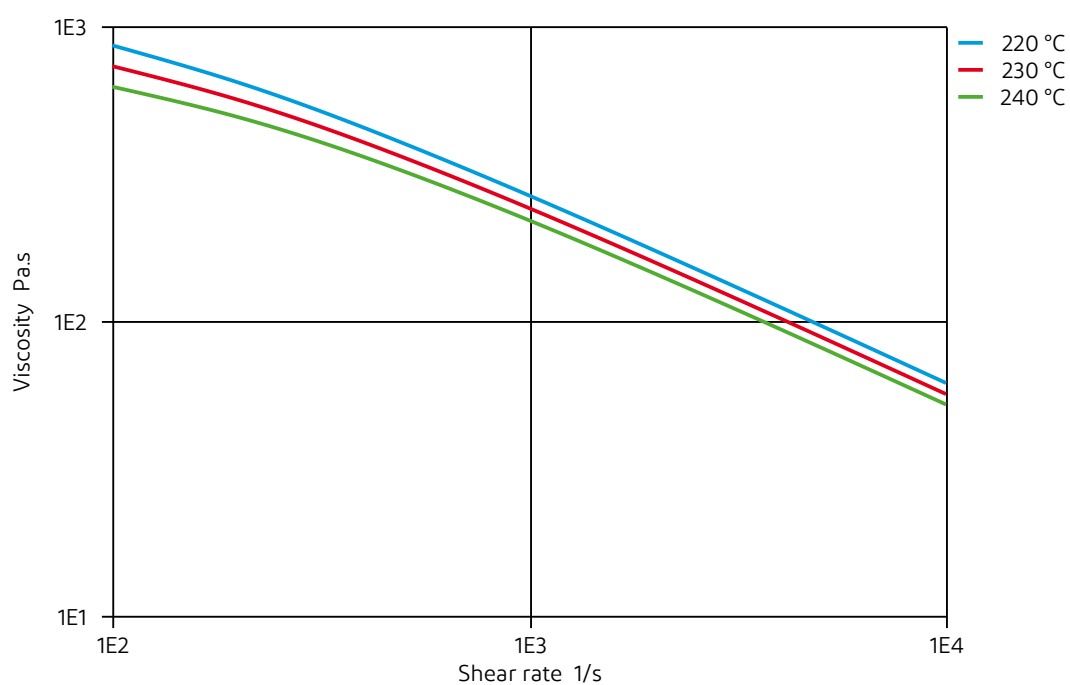

Hytrel[®] 5556

THERMOPLASTIC POLYESTER ELASTOMER

Shearstress-shear rate

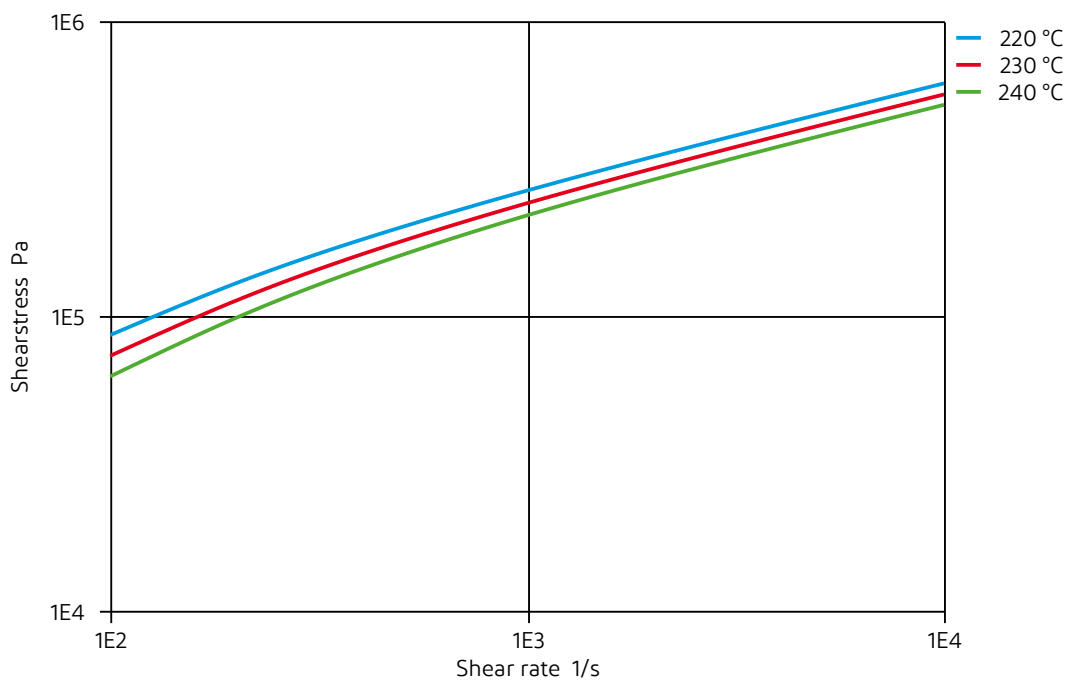




Hytrel[®] 5556

THERMOPLASTIC POLYESTER ELASTOMER

Dynamic Tensile modulus-temperature

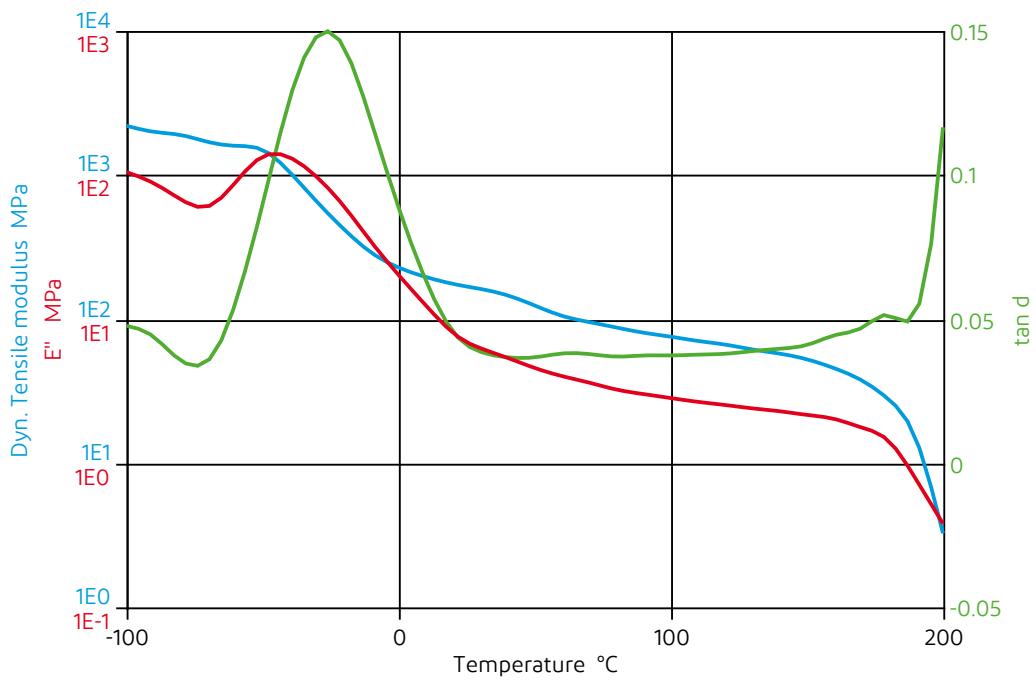




Hytrel[®] 5556

THERMOPLASTIC POLYESTER ELASTOMER

Stress-strain

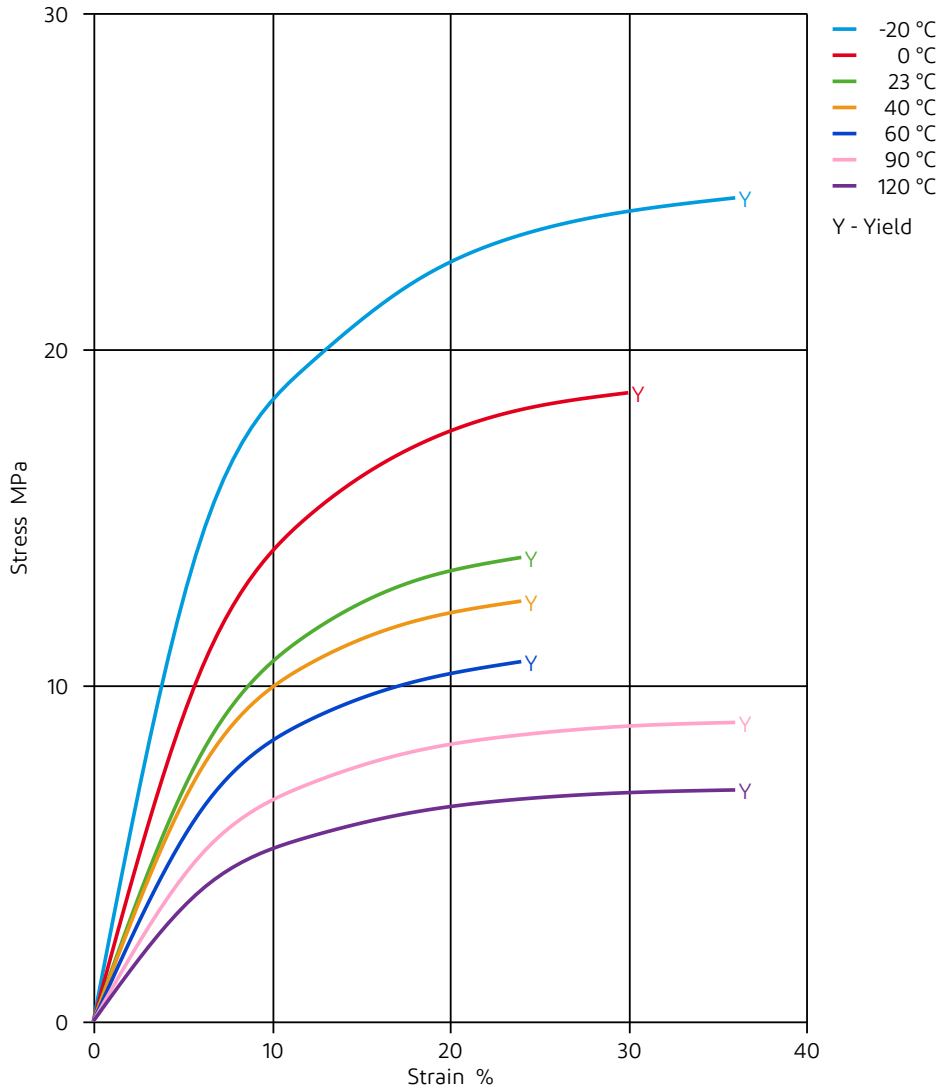




Hytrel[®] 5556

THERMOPLASTIC POLYESTER ELASTOMER

Secant modulus-strain

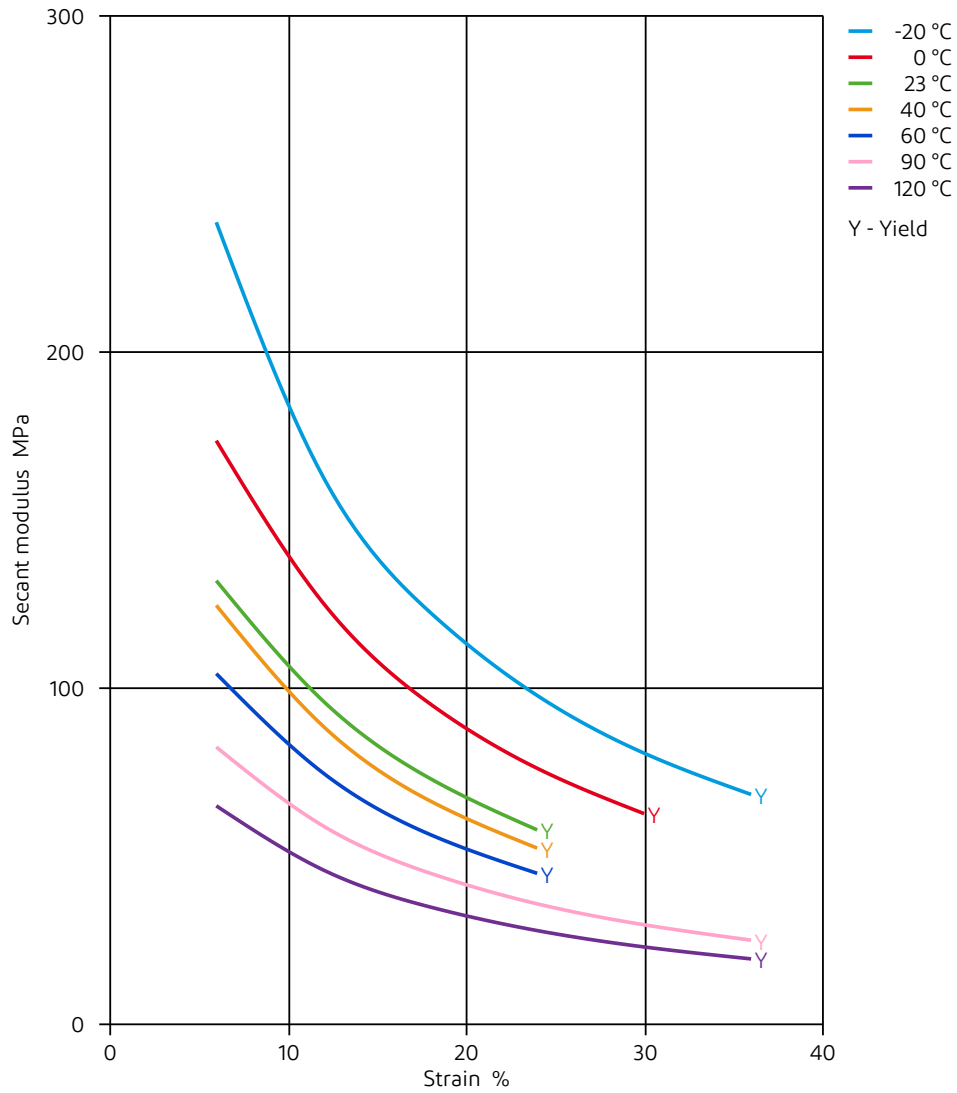




Hytrel[®] 5556

THERMOPLASTIC POLYESTER ELASTOMER

Stress-strain (isochronous) 23°C

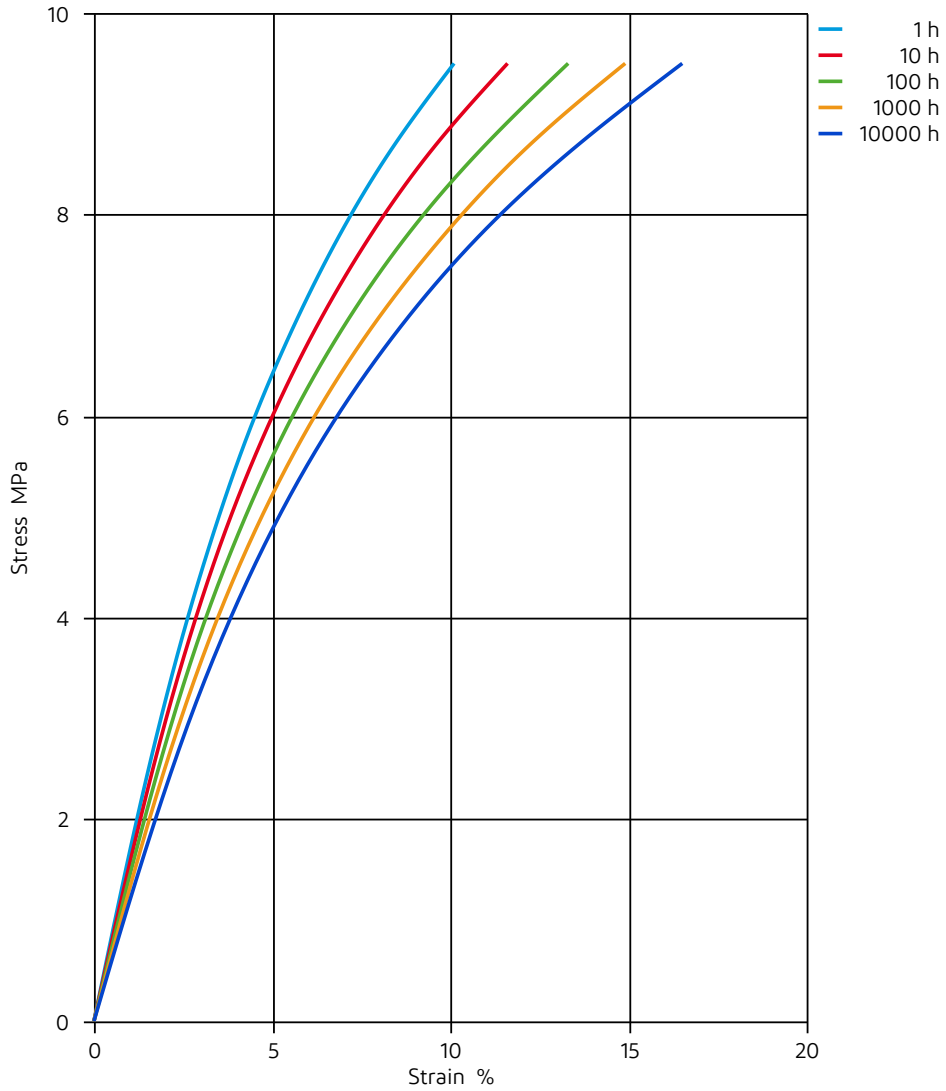




Hytrel[®] 5556

THERMOPLASTIC POLYESTER ELASTOMER

Creep modulus-time 23°C

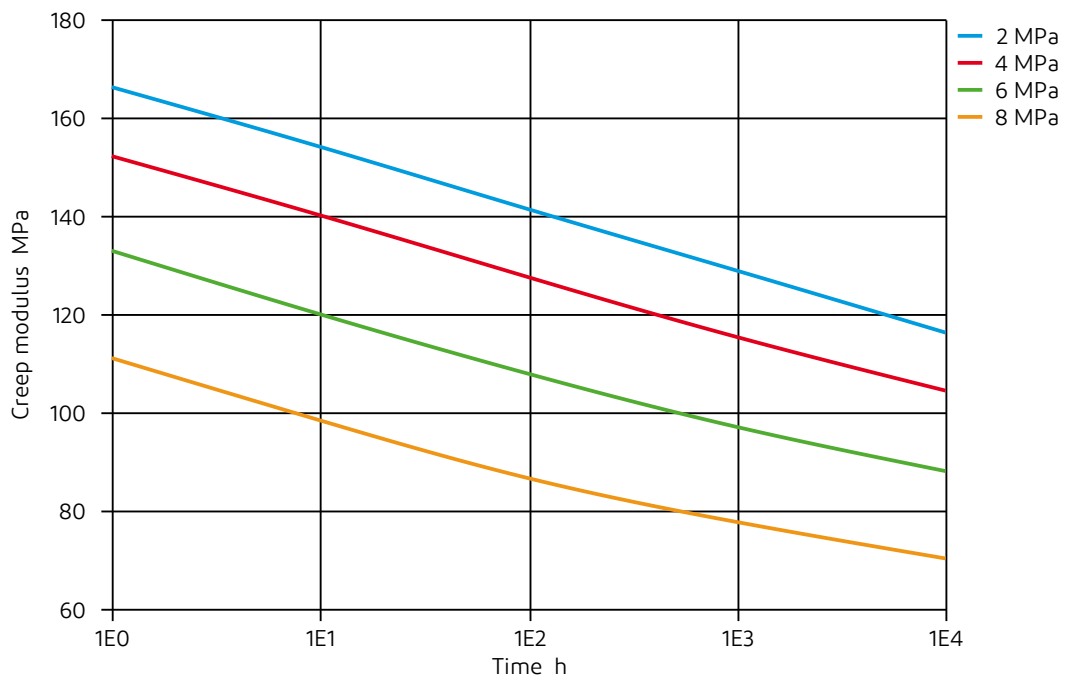




Hytrel[®] 5556

THERMOPLASTIC POLYESTER ELASTOMER


Stress-strain (isochronous) 40°C

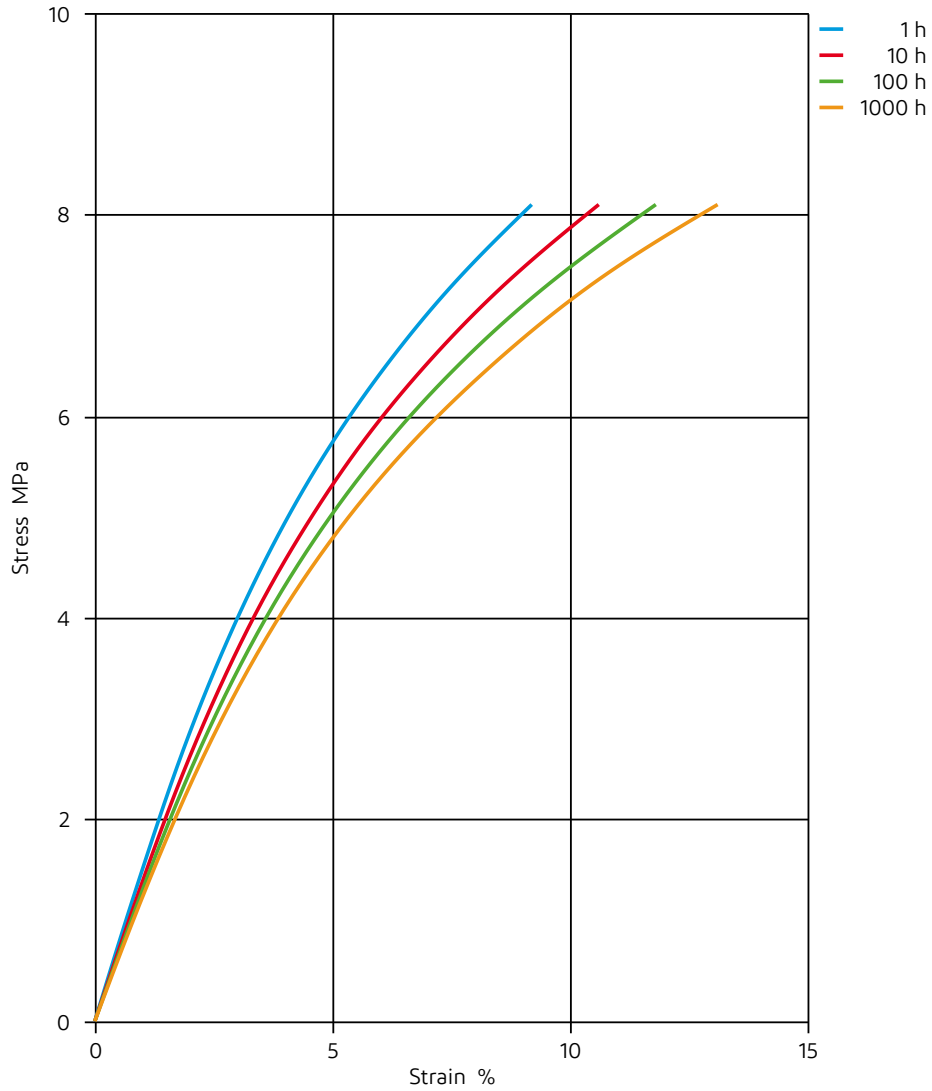

Hytrel[®] 5556

THERMOPLASTIC POLYESTER ELASTOMER

Creep modulus-time 40°C

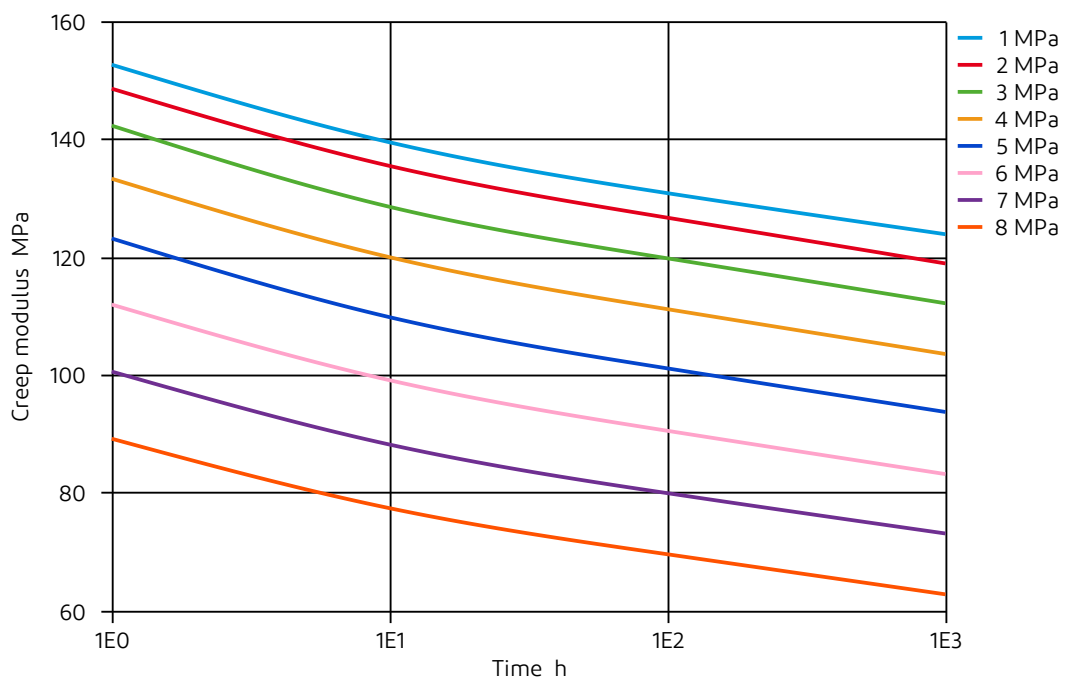




Hytrel[®] 5556

THERMOPLASTIC POLYESTER ELASTOMER

Stress-strain (isochronous) 80°C

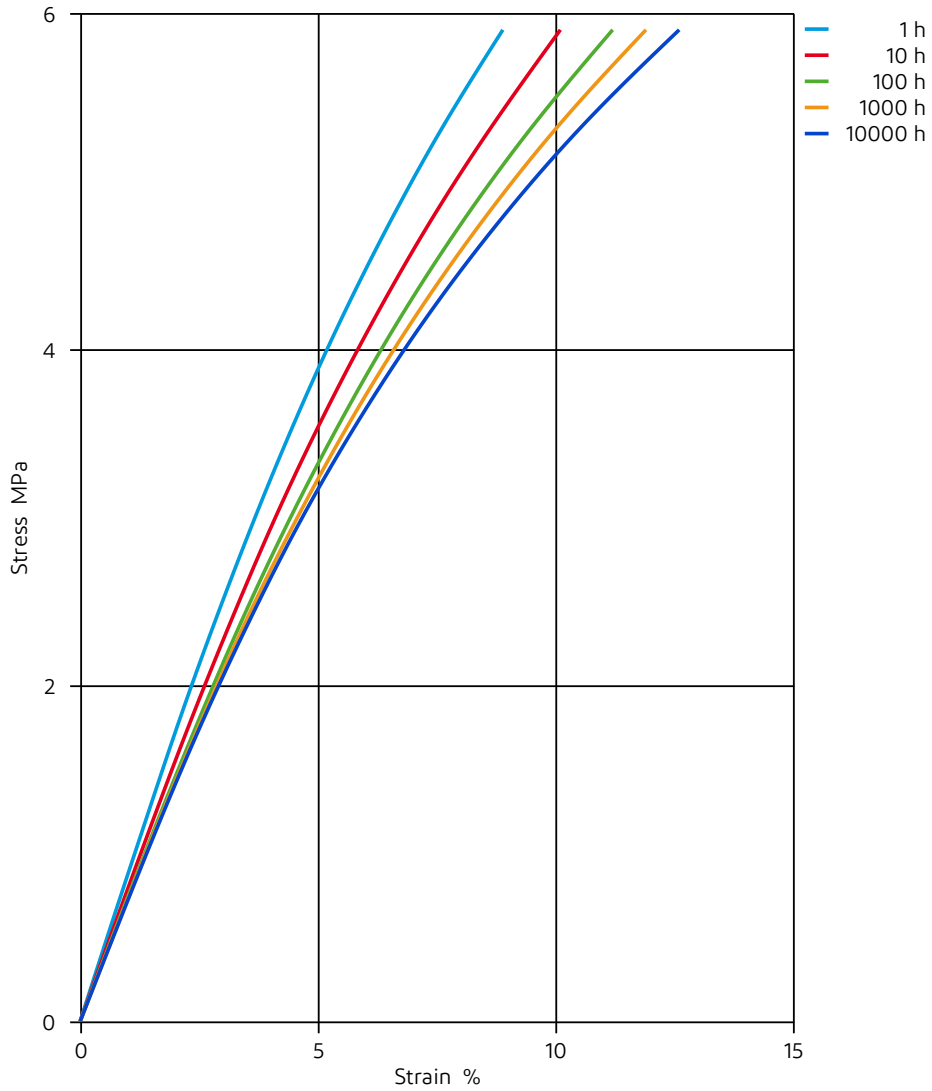




Hytrel[®] 5556

THERMOPLASTIC POLYESTER ELASTOMER


Creep modulus-time 80°C

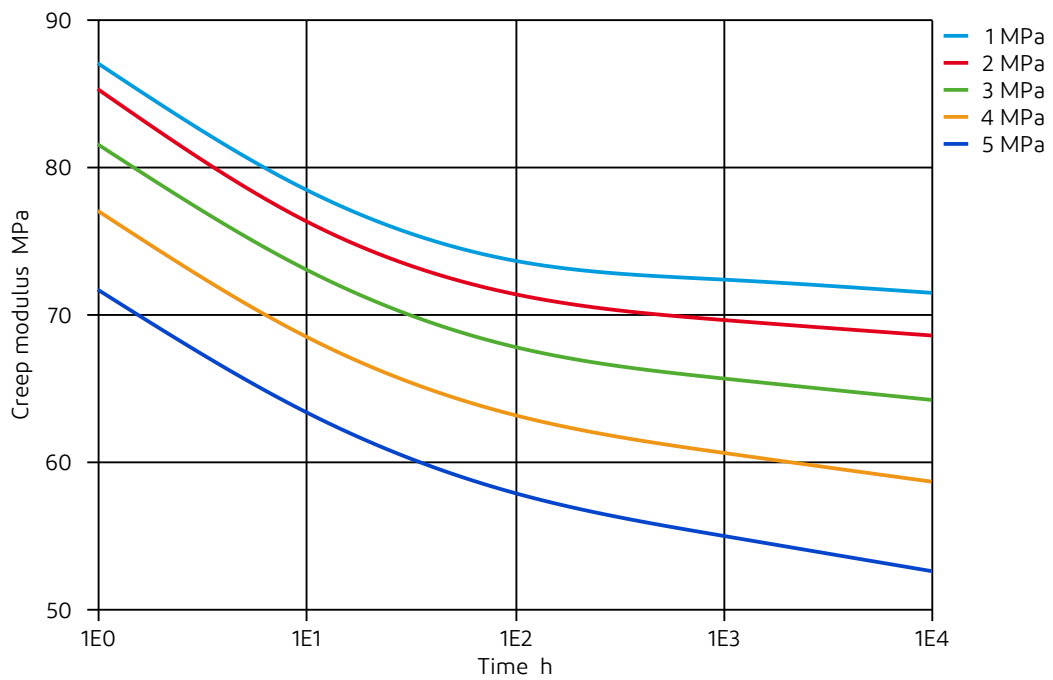

Hytrel[®] 5556

THERMOPLASTIC POLYESTER ELASTOMER

Specific volume-temperature (pvT)

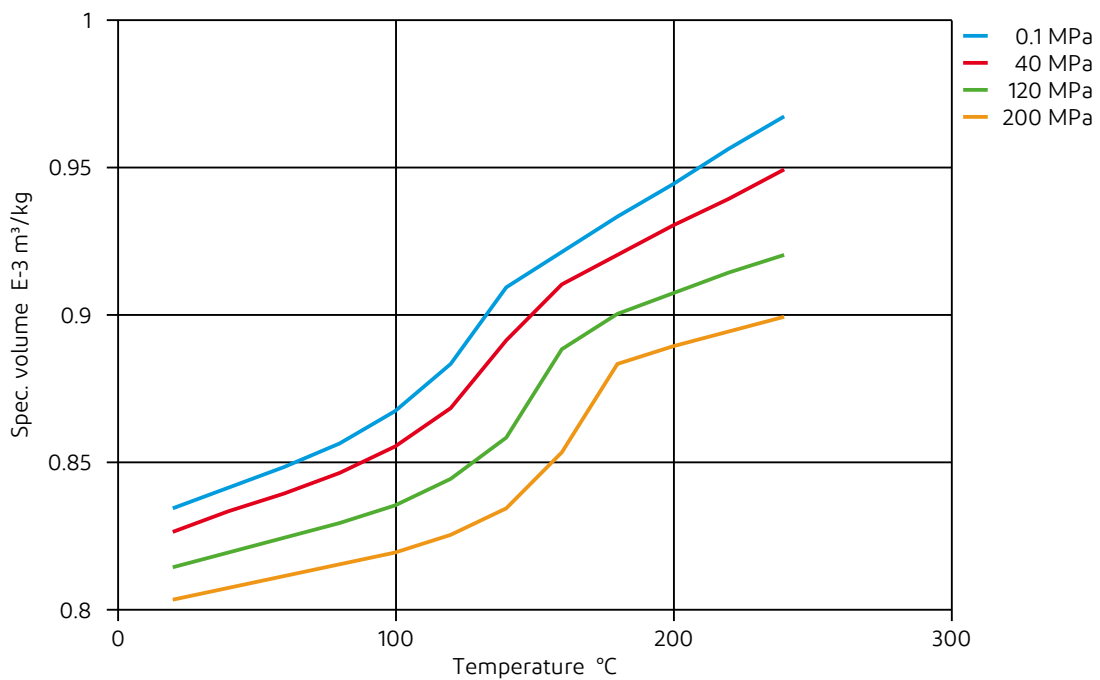




Hytrel[®] 5556

THERMOPLASTIC POLYESTER ELASTOMER

Stress-Strain (Flexible Materials)

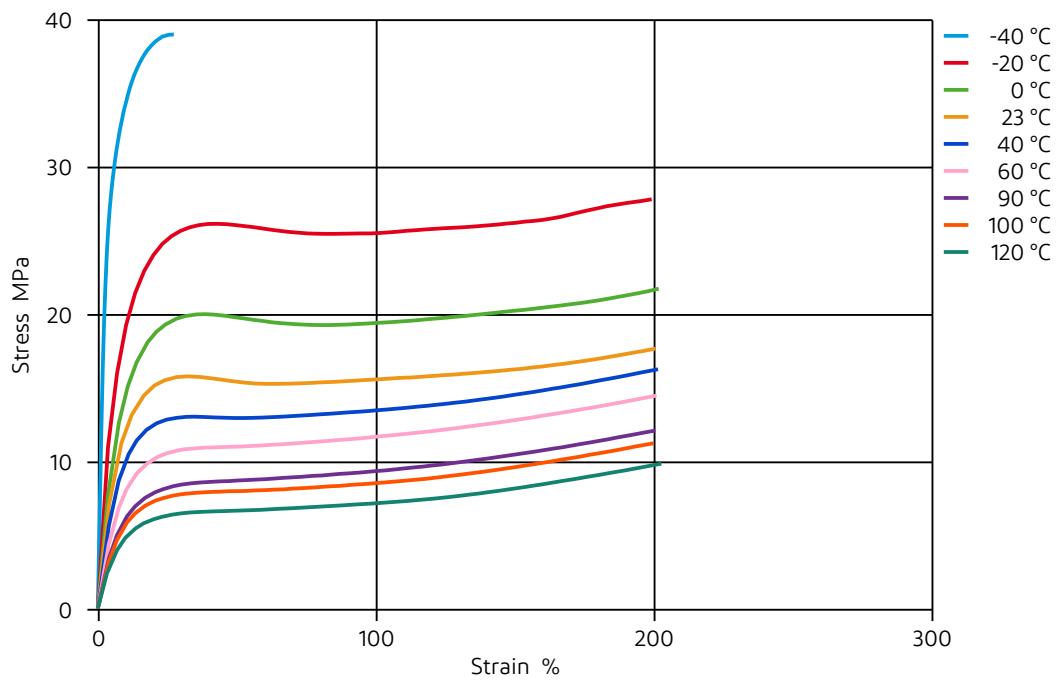

Hytrel[®] 5556

THERMOPLASTIC POLYESTER ELASTOMER

Chemical Media Resistance

Acids

- ✓ Acetic Acid (5% by mass), 23°C
- ✓ Citric Acid solution (10% by mass), 23°C
- ✓ Lactic Acid (10% by mass), 23°C
- ✗ Hydrochloric Acid (36% by mass), 23°C
- ✗ Nitric Acid (40% by mass), 23°C
- ✗ Sulfuric Acid (38% by mass), 23°C
- ✓ Sulfuric Acid (5% by mass), 23°C
- ✗ Chromic Acid solution (40% by mass), 23°C

Bases

- ✓ Sodium Hydroxide solution (35% by mass), 23°C
- ✓ Sodium Hydroxide solution (1% by mass), 23°C
- ✓ Ammonium Hydroxide solution (10% by mass), 23°C

Alcohols

- ✓ Isopropyl alcohol, 23°C
- ✓ Methanol, 23°C
- ✓ Ethanol, 23°C

Hydrocarbons

- ✓ n-Hexane, 23°C
- ✓ Toluene, 23°C
- ✓ iso-Octane, 23°C

Ketones

- ✗ Acetone, 23°C

Ethers

- ✗ Diethyl ether, 23°C

Mineral oils

- ✓ SAE 10W40 multigrade motor oil, 23°C
- ✗ SAE 10W40 multigrade motor oil, 130°C
- ✗ SAE 80/90 hypoid-gear oil, 130°C
- ✓ Insulating Oil, 23°C
- ✗ Motor oil OS206 304 Ref.Eng.Oil, ISP, 135°C
- ✗ Automatic hypoid-gear oil Shell Donax TX, 135°C
- ✗ Hydraulic oil Pentosin CHF 202, 125°C

Standard Fuels

- ✗ ISO 1817 Liquid 1 - E5, 60°C
- ✗ ISO 1817 Liquid 2 - M15E4, 60°C
- ✗ ISO 1817 Liquid 3 - M3E7, 60°C
- ✗ ISO 1817 Liquid 4 - M15, 60°C
- ✓ Standard fuel without alcohol (pref. ISO 1817 Liquid C), 23°C
- ✓ Standard fuel with alcohol (pref. ISO 1817 Liquid 4), 23°C



Hytrel® 5556

THERMOPLASTIC POLYESTER ELASTOMER

- ✓ Diesel fuel (pref. ISO 1817 Liquid F), 23°C
- ✓ Diesel fuel (pref. ISO 1817 Liquid F), 90°C
- ✗ Diesel fuel (pref. ISO 1817 Liquid F), >90°C

Salt solutions

- ✓ Sodium Chloride solution (10% by mass), 23°C
- ✗ Sodium Hypochlorite solution (10% by mass), 23°C
- ✓ Sodium Carbonate solution (20% by mass), 23°C
- ✓ Sodium Carbonate solution (2% by mass), 23°C
- ✓ Zinc Chloride solution (50% by mass), 23°C

Other

- ✓ Ethyl Acetate, 23°C
- ✗ Hydrogen peroxide, 23°C
- ✗ DOT No. 4 Brake fluid, 130°C
- ✗ Ethylene Glycol (50% by mass) in water, 108°C
- ✓ 50% Oleic acid + 50% Olive Oil, 23°C
- ✓ Water, 23°C
- ✓ Water, 90°C
- ✓ Phenol solution (5% by mass), 23°C

Symbols used:

- ✓ possibly resistant
Defined as: Supplier has sufficient indication that contact with chemical can be potentially accepted under the intended use conditions and expected service life. Criteria for assessment have to be indicated (e.g. surface aspect, volume change, property change).
- ✗ not recommended - see explanation
Defined as: Not recommended for general use. However, short-term exposure under certain restricted conditions could be acceptable (e.g. fast cleaning with thorough rinsing, spills, wiping, vapor exposure).

The information set forth herein is furnished free of charge, is based on technical data that DuPont believes to be reliable, and represents typical values that fall within the normal range of properties. This information relates only to the specific material designated and may not be valid for such material used in combination with other materials or in other processes. It is intended for use by persons having technical skill, at their own discretion and risk. This information should not be used to establish specification limits nor used alone as the basis of design. Handling precaution information is given with the understanding that those using it will satisfy themselves that their particular conditions of use present no health or safety hazards and comply with applicable law. Since conditions of product use and disposal are outside our control, we make no warranties, express or implied, and assume no liability in connection with any use of this information. As with any product, evaluation under end-use conditions prior to specification is essential. Nothing herein is to be taken as a license to operate or a recommendation to infringe on patents.

CAUTION: Do not use DuPont materials in medical applications involving implantation in the human body or contact with internal body fluids or tissues unless the material has been provided from DuPont under a written contract or other acknowledgement that is consistent with the DuPont policy regarding medical applications and expressly acknowledges the contemplated use. For further information, please contact your DuPont representative.

DuPont's sole warranty is that our products will meet our standard sales specifications in effect at the time of shipment. Your exclusive remedy for breach of such warranty is limited to refund of purchase price or replacement of any product shown to be other than as warranted. TO THE FULLEST EXTENT PERMITTED BY APPLICABLE LAW, DUPONT SPECIFICALLY DISCLAIMS ANY OTHER EXPRESS OR IMPLIED WARRANTY OF FITNESS FOR A PARTICULAR PURPOSE, MERCHANTABILITY, OR NON-INFRINGEMENT. DUPONT DISCLAIMS LIABILITY FOR ANY SPECIAL, INCIDENTAL, OR CONSEQUENTIAL DAMAGES.